

ADOPTION NOTICE

SAE-AS81935, "BEARINGS, PLAIN, ROD END, SELF-ALIGNING, SELF-LUBRICATING, GENERAL SPECIFICATION FOR", was adopted on 23-APR-98 for use by the Department of Defense (DoD). Proposed changes by DoD activities must be submitted to the DoD Adopting Activity: Commander, Naval Air Warfare Center, Aircraft Division, Code 414100B120-3, Highway 547, Lakehurst, NJ 08733-5100. Copies of this document may be purchased from the Society of Automotive Engineers 400 Commonwealth Drive Warrendale, Pennsylvania, United States, 15096-0001. <http://www.sae.org/>

Custodians:

Army - AV
Navy - AS
Air Force - 99

Adopting Activity:

Navy - AS

Reviewer Activities:

Army - AR, AT, MI
Navy - SH
Air Force - 11
DLA - GS

FSC 3120

DISTRIBUTION STATEMENT A: Approved for public release; distribution is unlimited.

Submitted for recognition as an American National Standard

**Bearings, Plain, Rod End, Self-Aligning, Self-Lubricating,
General Specification For**

NOTICE

This document has been taken directly from U.S. Military Specification MIL-B-81935A, Amendment 1 and contains only minor editorial and format changes required to bring it into conformance with the publishing requirements of SAE technical standards. Any part numbers established by the original specification remain unchanged and may not reflect the document number of the SAE Standard.

The original Military Specification was adopted as an SAE standard under the provisions of the SAE Technical Standards Board (TSB) Rules and Regulations (TSB 001) pertaining to accelerated adoption of government specifications and standards. TSB rules provide for (a) the publication of portions of unrevised government specifications and standards without consensus voting at the SAE Committee level, and (b) the use of the existing government specification or standard format.

Under Department of Defense Policies and Procedures, any qualification requirements and associated qualified products lists are mandatory for DoD contracts. Any material relating to Qualified Products Lists (QPL's) has not been adopted by SAE and is not part of this SAE technical document.

1. SCOPE:

1.1 Scope:

This specification covers plain rod end bearings which are self-aligning and self-lubricating by incorporating polytetrafluoroethylene (PTFE) in a liner between the ball and outer ring for use in the temperature range -65°F to +325°F.

1.2 Classification:

Bearings shall be of the following classes, as specified (see 6.2):

Class 1 - Externally threaded shank

Class 2 - Internally threaded shank

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

Copyright 1997 Society of Automotive Engineers, Inc.
All rights reserved.

Printed in U.S.A.

QUESTIONS REGARDING THIS DOCUMENT:
TO PLACE A DOCUMENT ORDER:
SAE WEB ADDRESS

(412) 772-8510
(412) 776-4970
<http://www.sae.org>

FAX: (412) 776-0243
FAX: (412) 776-0790

Distributed under license from the IHS Archive

SAE AS81935

2. APPLICABLE DOCUMENTS:

2.1 Government documents:

- 2.1.1 Specifications, standards and handbooks: The following specifications, standards and handbooks form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DoDISS), and supplement thereto, cited in the solicitation.

SPECIFICATIONS

FEDERAL

QQ-P-416 Plating, Cadmium (Electrodeposited).

MILITARY

MIL-P-116 Preservation, Methods of.

MIL-B-197 Bearings, Anti-Friction, Associated Parts and Sub-Assemblies, Packaging of.

MIL-S-8879 Screw Threads, Controlled Radius Root With Increased Minor Diameter, General Specification for.

MIL-B-81820 Bearing, Plain, Self-Aligning, Self-Lubricating, Low Speed Oscillation.

MIL-B-81935/1 Bearing, Plain, Rod End, Self-Aligning, Self-Lubricating, Externally Threaded, -65°F to +325°F.

MIL-B-81935/2 Bearing, Plain, Rod End, Self-Aligning, Self-Lubricating, Wide, Internally Threaded, -65°F to +325°F.

MIL-B-81935/3 Locking Device, Rod End.

MIL-B-81935/4 Bearing, Plain, Rod End, Self-Aligning, Self-Lubricating, Narrow, Externally Threaded, -65°F to +325°F.

MIL-B-81935/5 Bearing, Plain, Rod End, Self-Aligning, Self-Lubricating, Narrow, Internally Threaded, -65°F to +325°F.

SAE AS81935

2.1.1 (Continued):

STANDARDS

MILITARY

DOD-STD-100	Engineering Drawing Practices.
MIL-STD-105	Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129	Marking for Shipment and Storage.
MIL-STD-130	Identification Marking of U. S. Military Property.
MIL-STD-1949	Inspection, Magnetic Particle.
MS1401	Bearing, Plain, Self-Lubricating, Self-Aligning, Low Speed, Narrow, Grooved Outer Ring, -65°F to +325°F.
MS14103	Bearing, Plain, Self-Lubricating, Self-Aligning, Low Speed, Wide, Grooved Outer Ring, -65°F to +325°F.

(Copies of specifications, standards, handbooks, drawings, publications and other Government documents required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting activity.)

2.2 Other publications:

The following document(s) forms a part of this specification to the extent specified herein. Unless otherwise specified, the issues of the documents which are DoD adopted shall be those listed in the issue of the DoDISS specified in the solicitation. Unless otherwise specified, the issues of documents not listed in the DoDISS shall be the issue of the nongovernment documents which is current on the date of the solicitation.

American National Standards Institute

ANSI B46.1 Surface Texture, Surface Roughness, Waviness and Lay.

(Application for copies should be addressed to the American National Standards Institute, 1430 Broadway, New York, NY 10018.)

SAE AS81935

2.2 (Continued):

Uniform Classification Committee

Uniform Freight Classification Rules

(Application for copies of the above publication should be addressed to the Uniform Classification Committee, 202 Chicago Union Station, Chicago, IL 60606.)

(Nongovernment standards and other publications are normally available from the organizations which prepare or which distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence:

In the event of a conflict between the text of this specification and the references cited herein (except for associated detail specifications, specification sheets or MS standards), the text of this specification shall take precedence. Nothing in this specification, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS:

3.1 Specification sheets:

The individual item requirements shall be as specified herein and in accordance with the applicable specification sheet. In the event of any conflict between the requirements of this specification and the specification sheet, the latter shall govern.

3.2 Qualification:

Bearings furnished under this specification shall be products which are authorized by the qualifying activity for listing on the applicable Qualified Products List at the time set for opening of bids (see 4.4, 6.3 and 6.3.1).

3.2.1 Product design change: Any change in product design, description, materials or processing procedures will require requalification of the product to an extent determined by the qualifying activity. For the purposes of this specification "change in processing procedures" means a change in any of the following: (1) the company performing rod end body machining, (2) the company performing rod end body heat treating, or (3) the company performing thread forming.

SAE AS81935

3.3 Bearing cartridge:

The bearing cartridge used in these rod ends shall be in accordance with MS14101 or MS14103, shall be qualified to MIL-B-81820 and shall have been subjected to and passed the Quality Conformance Tests of Section 4.4 of MIL-B-81820. If the bearing cartridge used in these rod ends was produced by another manufacturer, the Department of Defense regulations and policies regarding rebranding of products shall apply. These regulations state that when a company wishes to supply a qualified product carrying its own brand designations, but which is manufactured by another firm, the manufacturer shall be requested by the company to certify that the company is authorized to rebrand and distribute the product with its own brand designation. Additional information about these regulations may be obtained from the Naval Air Engineering Center, Systems Engineering and Standardization Department, Code 5311, Lakehurst, NJ 08733-5100.

3.4 Materials:

The rod end body materials shall be in accordance with the applicable military specification sheet.

3.4.1 Cadmium plating: The alloy steel rod end bodies shall be cadmium plated in accordance with QQ-P-416, Type II, Class 2. The plated bodies shall be heated to a temperature of $375^{\circ} \pm 25^{\circ}\text{F}$ within 4 hours after plating but before the chromate treatment and magnetic particle inspection, and held at this temperature for a minimum of 3 hours, after which the bodies shall be allowed to cool normally at room temperature.

3.4.2 Lubrication: Initial grease or oil lubrication of the bearing cartridge will not be permitted. Use of anti-fretting material between the bearing cartridge and the rod end body is permitted.

3.5 Design and construction:

The design of the bearing shall conform to the requirements of MIL-B-81935/1, MIL-B-81935/2, MIL-B-81935/4 or MIL-B-81935/5. Construction shall be such that all relative motion will be between the liner and ball. Except as otherwise specified, the details of the working parts shall be optional.

3.5.1 Dimensions and tolerances: Dimensions and tolerances shall be as specified on the applicable military specification sheet. Dimensions not shown shall be at the option of the manufacturer.

3.5.2 Surface texture: Surface textures shall be in accordance with the applicable military specification sheet and ANSI B46.1. Bearings shall be free of any defects which may be detrimental to satisfactory installation, performance or bearing life, as defined by this specification.

3.5.3 Hardness: Each rod end body shall be tested for hardness as specified in 4.7.5. Alloy steel rod ends shall be tested after heat treatment but before plating. Only rod end bodies with Rockwell readings in the range allowed by the applicable military specification sheet shall be acceptable.

SAE AS81935

3.5.4 Threads:

3.5.4.1 Class 1 rod ends: Dimensions, form and contour shall conform to MIL-S-8879. Threads shall be rolled after heat treatment. Rerolling of threads to correct dimensional deficiencies shall not be permitted.

3.5.4.2 Class 2 rod ends: Threads shall conform to MIL-S-8879.

3.5.5 Magnetic particle inspection: All rod end bodies shall be examined by magnetic particle inspection as specified in 4.7.6.1. Any rod end bodies having discontinuities equal to or exceeding the limitations specified herein shall be rejected. Care must be exercised to avoid confusing cracks, as described herein, with other discontinuities.

3.5.5.1 Cracks: Rod end bodies shall be free of cracks in any direction or location. A crack is defined as a clean crystalline break passing through the grain or grain boundary without the inclusion of foreign elements.

3.5.5.2 Laps and seams: Rod end bodies may possess laps and seams, except in locations specified in 3.5.5.4 and 3.5.5.5. Except as noted, the depths shall not exceed the amounts specified in Table I. A lap is a surface defect appearing as a seam caused by folding over hot metal fins or sharp corners and then rolling or forging them into the surface, but not welding them. A seam is an unwelded fold or lap which appears as an opening in the raw material as received from the source.

TABLE I. Discontinuity depths. ^{1/}

Bearing Size	-4 and -5	-6	-7	-8 thru -16
Seam Depth (inch) (maximum)	0.005	0.006	0.007	0.008

^{1/} Depth of discontinuity shall be measured normal to the surface at the point of greatest penetration.

3.5.5.3 Inclusions: Rod end bodies shall show no evidence of surface or subsurface inclusions at the thread root, hoop-to-shank fillet or in the 3 to 6 to 9 o'clock positions of the hoop (see Figure 1) when inspected in accordance with 4.7.6. Small inclusions in other parts of the rod end body not indicative of unsatisfactory material quality, shall not be cause for rejection.

3.5.5.4 Hoop and hoop-to-shank fillet discontinuities (seams and folds): The rod end body shall not have seams or folds in the 3 to 6 to 9 o'clock positions of the hoop or in the hoop-to-shank fillet. Seams or folds in the 9 to 12 to 3 o'clock positions of the hoop not exceeding the limits of Table I shall not be cause for rejection.

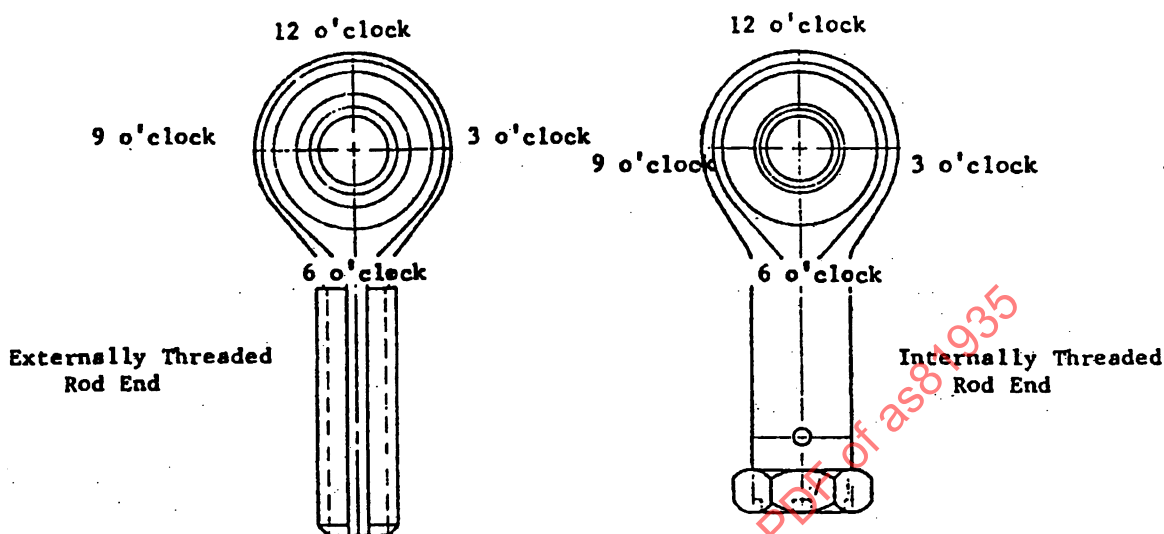



FIGURE 1. Hoop position designations.

3.5.5.5 Thread discontinuities (laps, seams and surface irregularities): Threads shall have no multiple or single laps at the root or on the sides (Figure 2), except that laps are permissible at the crest which do not exceed 25 percent of basic thread depth, and on the sides outside the pitch diameter (see Figure 3). Deviation from the thread contour is permissible at the crest of the thread as shown in Figure 3. The incomplete thread at each end of the thread may also deviate from contour.

3.6 Performance:


- 3.6.1 Ultimate static load: No fracture of the rod end body shall occur when the ultimate static load specified on the applicable rod end military specification sheet is applied in accordance with 4.7.1.
- 3.6.2 Axial static proof load: No pushout of the bearing cartridge from the rod end body shall occur when the axial proof load on the applicable military specification sheet is applied as specified in 4.7.2.
- 3.6.3 Fatigue load: The rod end bearings shall be capable of withstanding a minimum of 50,000 cycles of loading when tested in accordance with 4.7.3.
- 3.6.4 Self-alignment: The bearing shall be self-aligning and permit the angular displacement specified on the applicable military specification sheet.
- 3.6.5 No-load rotational breakaway torque: When tested in accordance with 4.7.4, the no-load breakaway torque shall be within the limits of the values specified on the applicable rod end military specification sheet.

SAE AS81935

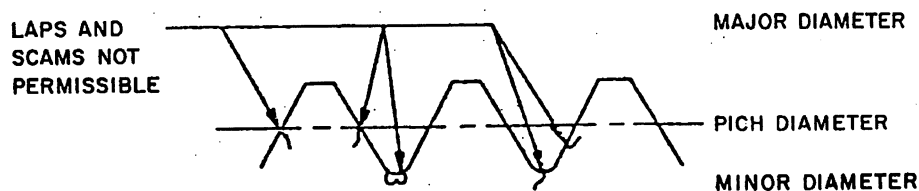

Note: For limits see 3.5.5.2 and 3.5.5.3.

FIGURE 2. Nonpermissible laps, seams and surface irregularities.

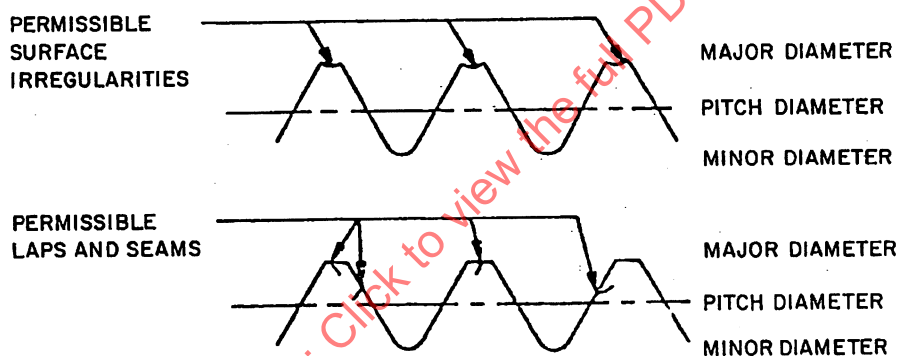

Note: For limits see 3.5.5.5.

FIGURE 3. Permissible laps, seams and surface irregularities.

3.7 Interchangeability.

All parts having the same manufacturer's part number shall be directly and completely interchangeable with each other with respect to installation and performance. The drawing number requirements of DOD-STD-100 shall govern changes in the manufacturers' part numbers.

3.8 Identification of product:

Each bearing shall be permanently and legibly marked with the military identifying part number, the manufacturer's name or trademark, and manufacturer's part number. Where practicable, identification shall appear on the side face of the rod end body; otherwise identification shall appear on the periphery of the rod end body. Metal impression stamping is prohibited. (Marking in accordance with MIL-STD-130.)

SAE AS81935

3.9 Workmanship:

The bearing shall be free of tool marks, chatter waves, rust, grinding scratches, pits, cracks or any other defects that may adversely affect their serviceability.

4. QUALITY ASSURANCE PROVISIONS:

4.1 Responsibility for inspection:

Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance: All items must meet all requirements of Sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.2 Qualification test records:

The manufacturer shall maintain a record showing quantitative results for all tests required by this specification. This record shall be available to the purchaser and shall be signed by an authorized representative of the manufacturer or the testing laboratory, as applicable.

4.3 Classification of inspection:

The examination and testing of the bearings shall be classified as:

- a. Qualification inspection (4.4).
- b. Quality conformance inspection (4.5).

SAE AS81935

4.4 Qualification inspections:

- 4.4.1 Sampling instructions: Qualification inspection samples shall consist of ten bearings of sizes -6, -8, -12 for each class (1 and 2) for which qualification is desired. The test bearings shall be furnished by the manufacturer. The bearings shall be identified and forwarded to the Naval Air Development Center, Code 6061, Warminster, PA 18974-5000.

Approval of the bearing sizes in column I will extend to approval of the corresponding sizes in column II.

TABLE II. Order of qualifying bearings

I	II
MIL-B-81935/1-06	-03, -04, -05, -06
MIL-B-81935/1-08	-07, -08, -10
MIL-B-81935/1-12	-12, -14, -16
MIL-B-81935/2-06	-03, -04, -05, -06
MIL-B-81935/2-08	-07, -08, -10
MIL-B-81935/2-12	-12, -14, -16

- 4.4.2 Certified test report: The manufacturer shall furnish a certified test report showing the manufacturer's product satisfactorily conforms to this specification. The test report shall include, as a minimum, actual results of the tests specified herein. When the report is submitted, it shall be accompanied by a dated drawing which completely describes the manufacturer's product by specifying all dimensions and tolerances, the part number of the bearing cartridge, anti-fretting material if used, coating or plating, and heat treatment. The manufacturer's part number for each size shall be included on the drawing.

SAE AS81935

- 4.4.3 Inspections: Qualification inspections shall include all the examinations and tests of this specification. The minimum number of samples per test shall be in accordance with Table III.

TABLE III. Qualification inspection samples.

Examination and Test	Paragraph No.	Samples To Be Tested
Examination of product	4.6.1	5
Preparation for delivery	4.6.2	5
Ultimate static load	4.7.1	3
Axial static proof load	4.7.2	<u>1</u> /3
Fatigue load	4.7.3	3

1/ Satisfactory test results for Class 1 bearings will apply toward qualification of Class 1 and Class 2.

- 4.4.4 Retention of qualification: The retention of qualification shall consist of periodic verification and shall be by certification unless otherwise specified by the activity responsible for the Qualified Products List and shall be at intervals of not more than two years.

4.5 Quality conformance inspections:

- 4.5.1 Bearing cartridge inspection: The bearing cartridge installed in the rod end body shall meet the requirements of paragraph 3.3. The bearing supplier shall maintain and supply to the purchaser upon demand:
- Certified copies of all records of quality conformance tests specified in 4.4 of MIL-B-81820.
 - Certification that the materials and manufacturing procedures used in producing the bearing cartridge are the same as those of the bearings originally qualified.

SAE AS81935

4.5.2 Rod end bearing inspection: The quality conformance inspections of the bearings shall consist of the following examinations and tests to determine conformance of the bearings to the requirements of this specification and the applicable military specification sheet. The bearing supplier shall supply written certification the bearings conform to these requirements with each inspection lot.

a. Dimensions	3.5.1	4.6.1
b. Identification of product	3.8	4.6.1
c. Workmanship	3.9	4.6.1
d. Preparation for delivery		4.6.2
e. No-load rotational breakaway torque	3.6.5	4.7.4
f. Hardness	3.5.3	4.7.5
g. Magnetic particle inspection	3.5.5	4.7.6

4.5.3 Inspections: The bearing manufacturer shall be responsible for accomplishing the quality conformance inspections specified herein.

4.5.4 Lot: The lot definition, formation and size shall be in accordance with MIL-STD-105.

4.5.5 Sampling: The sample bearing shall be selected in accordance with MIL-STD-105, inspection level II, acceptable quality level of 1.0 percent, except that inspection for no-load rotational breakaway torque, hardness and magnetic inspection of the rod end body shall be 100 percent.

4.6 Examinations:


4.6.1 Examination of product: The bearings shall be examined to determine conformance to the requirements of this specification and the applicable standard for material, plating, dimensions, finish, identification of product, workmanship and requirements not covered by tests.

4.6.2 Inspection of preparation for delivery: Preservation, packaging, packing and marking shall be inspected to determine conformance of Section 5.

4.7 Test methods:

Unless otherwise specified, all tests shall be conducted at room temperature.

4.7.1 Ultimate static load: The bearing shall be installed in a test fixture as shown on Figure 4, using a 0.0000 to 0.0015-inch loose fit for the shaft. The appropriate ultimate static load specified on the rod end military specification sheet shall be applied at the rate of one percent per second.

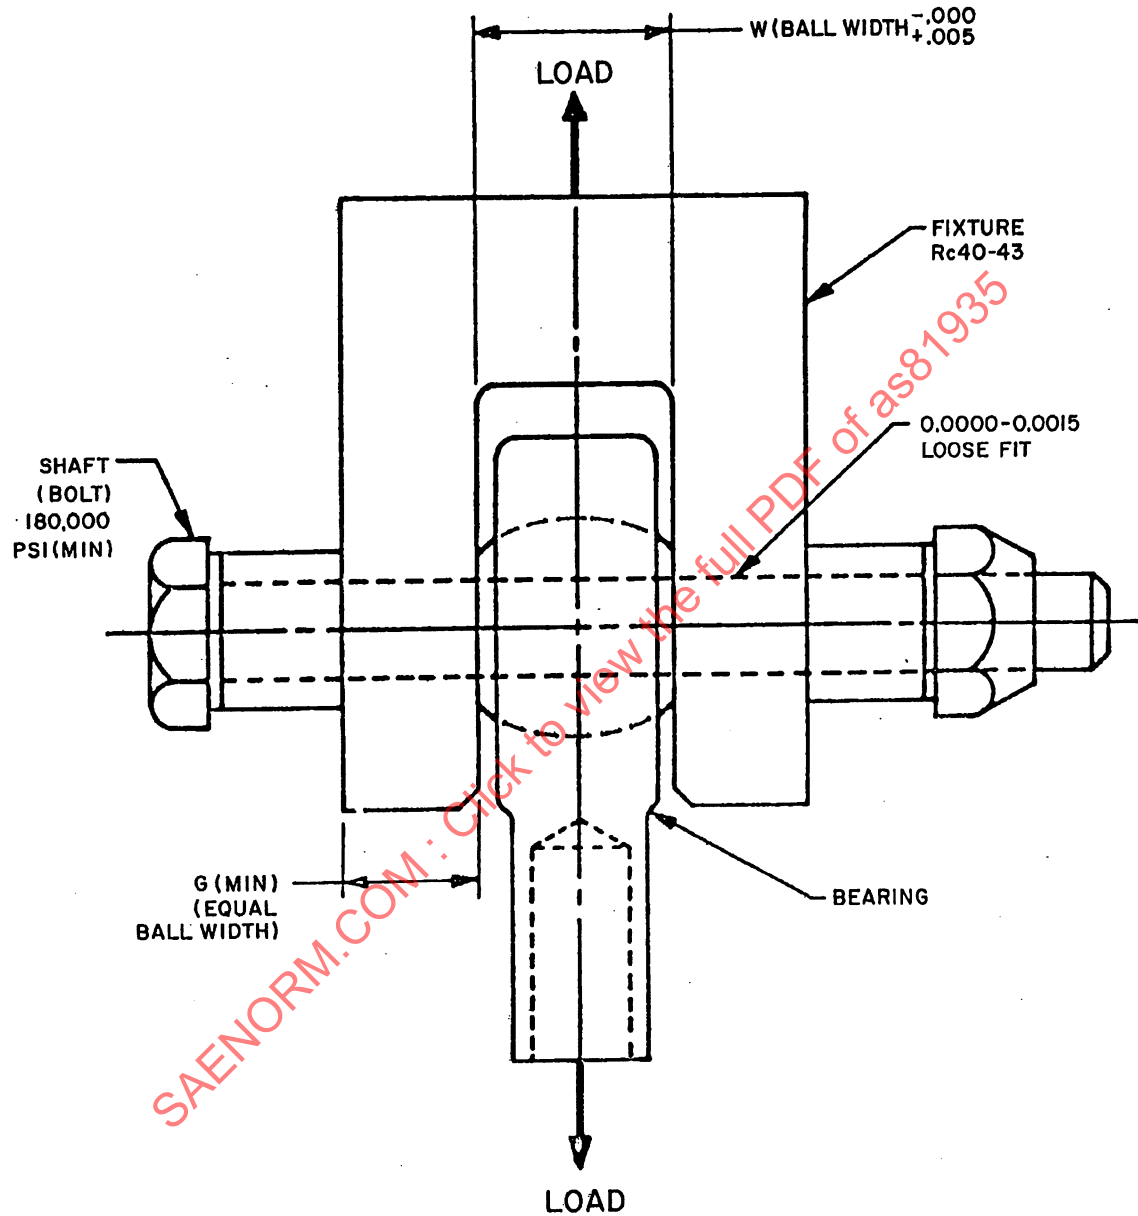

DIMENSIONS IN INCHES

FIGURE 4. Ultimate and fatigue test fixture.