



SURFACE VEHICLE RECOMMENDED PRACTICE

J1402™

APR2025

Issued 1942-01
Revised 2025-04

Superseding J1402 OCT2017

Automotive Air Brake Hose and Hose Assemblies

RATIONALE

During the Five-Year Review, the document was updated as follows: In 2.1.1, removed non-applicable standard SAE J1401; added 2.1.3 ARPM Publication reference for Hose Manufacturers Identification Codes and updated 6.1 with ARPM information; updated document to SAE standard by removing INCH references throughout (Tables 1 and 2, 4.2, and Tables 3, 4, and 6); and in 7.2.1.2, added -54°C low temperature testing protocol and also referenced the temperature change in Section 1 Scope.

1. SCOPE

This SAE Recommended Practice covers minimum requirements for air brake hose assemblies made from reinforced elastomeric hose and suitable fittings for use in automotive air brake systems, including flexible connections from frame to axle, tractor to trailer, trailer to trailer, and other unshielded air lines with air pressures up to 1 MPa, that are exposed to potential pull or impact. This hose is not to be used where temperatures, external or internal, fall outside the range of -40 to +100 °C. Provisions for extreme low temperature performance testing to -54 °C are included in the document.

2. REFERENCES

2.1 Applicable Documents

The following publications form a part of this specification to the extent specified herein. Unless otherwise indicated, the latest issue of SAE publications shall apply.

2.1.1 SAE Publications

Available from SAE International, 400 Commonwealth Drive, Warrendale, PA 15096-0001, Tel: 877-606-7323 (inside USA and Canada) or +1 724-776-4970 (outside USA), www.sae.org.

SAE J517 Hydraulic Hose

SAE Executive Standards Committee Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2025 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system, transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, or used for text and data mining, AI training, or similar technologies, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Tel: +1 724-776-4970 (outside USA)
Fax: 724-776-0790
Email: CustomerService@sae.org
http://www.sae.org

SAE WEB ADDRESS:

For more information on this standard, visit
https://www.sae.org/standards/content/J1402_202504/

2.1.2 ARPM Publications

Available from Association for Rubber Products Manufacturers, 732 Shadeland Station Way #285, Indianapolis, IN 46256, Tel: (317) 863-4072, www.arpminc.com.

Hose Manufacturer Identification Codes-Colored Yarn Assignments

2.1.3 ASTM Publications

Available from ASTM International, 100 Barr Harbor Drive, P.O. Box C700, West Conshohocken, PA 19428-2959, Tel: 610-832-9585, www.astm.org.

ASTM B117 Standard Test Method of Salt Spray (Fog) Testing

ASTM D380 Standard Test Methods for Rubber Hose

ASTM D413 Test Methods for Rubber Property - Adhesion to Flexible Substrate

3. HOSE CONSTRUCTIONS AND DIMENSIONS

There are four distinct hose constructions used for air brake hose assemblies made from reinforced elastomeric hose. All dimensions are in accordance with Tables 1 and 2.

Type A consists of an elastomeric tube, a fiber reinforcement and an elastomeric cover.

Type AI consists of an elastomeric tube, a wire or fiber reinforcement, and a fiber braid cover.

Type AII consists of an elastomeric tube, a wire or fiber reinforcement, and a fiber braid or elastomeric cover. This hose is dimensionally identical to SAE J517 100R5 hose.

Type AIII consists of an elastomeric tube, wire or fiber reinforcement, and a fiber braid or elastomeric cover.

Table 1 - Inside and outside diameters for Type A and AIII hoses

Metric Size	SAE Type A					SAE Type AIII				
	Dash Size (Ref)	Type A ID Min	Type A ID Max	Type A OD Min	Type A OD Max	Dash Size (Ref)	Type AIII ID Min	Type AIII ID Max	Type AIII OD Min	Type AIII OD Max
6.3	-4	5.8	6.9	15.1	16.7	-4	6.2	7.0	12.0	14.0
8	-5	7.3	8.5	16.7	18.3					
10	-6	8.9	10.1	18.3	19.8	-6	9.3	10.1	15.5	17.5
11.5	-7	10.3	11.9	19.8	21.4					
12.5 SP	-8	11.9	13.5	21.4	23.0					
12.5						-8	12.3	13.5	19.0	21.0
16	-10	15.1	16.7	26.2	27.8	-10	15.5	16.7	22.7	24.7

Note: All dimensions are in millimeters, unless otherwise specified.

NOTE: The sizes 6.3, 8, 10, 11.5, and 12.5 SP of Type A hose can be assembled with field attachable fittings if desired. These field attachable fittings are not the same as used with Types AI and AII hoses. AIII hoses are assembled with permanent crimp fittings only.

Table 2 - Inside and outside diameters for Type AI and All hoses

Metric Size	SAE Type AI and All Dash Size (Ref)	Type AI and All ID Min	Type AI and All ID Max	Type AI OD Min	Type AI OD Max	Type All OD Min	Type All OD Max
5	-4	4.8	5.5	12.0	13.0	12.7	13.7
6.3	-5	6.4	7.2	13.6	14.6	14.3	15.3
8	-6	7.9	8.7	15.1	16.2	16.7	17.6
11	-8	10.3	11.1	18.1	19.3	18.9	20.0
12.5	-10	12.7	13.7	20.5	21.7	22.8	24.0
16	-12	15.9	17.0	23.7	24.9	26.8	28.0

Note: All dimensions are in millimeters, unless otherwise specified.

4. FITTINGS

4.1 For Permanently Attached Fittings

When the hose is assembled with permanently attached fittings, the hose portion of the hose assembly shall conform to the dimensional requirements of Type A or All hose in Table 1 and AI or All hose in Table 2.

4.2 For Field Attachable Fittings

When the hose is assembled with field attachable fittings, the hose portion of the hose assembly shall conform to the dimensional requirements for all sizes of Type AI or All hose in Table 2 or shall conform to the dimensional requirements of 6.3, 8, 10, 11.5, and 12.5 SP Type A hose from Table 1.

NOTE: The sizes 6.3, 8, 10, 11.5, and 12.5 SP of Type A hose can be assembled with field attachable fittings if desired. These field attachable fittings are not the same as used with Types AI and All hoses.

5. MINIMUM BEND RADIUS

Table 3 contains the minimum bend radii recommended for vehicle installations.

Table 3 - Recommended minimum bend radius

Metric Size	SAE Type AI and All Dash Size (Ref)	Minimum Bend Radius to Inside of Bend (millimeters)
5	-4	50
6.3	-5	65
8	-6	75
10	--	90
11	-8	90
11.5	--	100
12.5 SP	--	100
12.5	-10	100
16	-12	115

6. IDENTIFICATION

6.1 Hose

Each hose manufacturer shall incorporate into the hose construction an identification yarn as assigned by the ARPM, Hose Manufacturer Identification Codes-Colored Yarn Assignments, Latest Edition.

Each air brake hose shall also be labeled in a color contrasting to that of the hose and labeling shall be repeated every 600 mm or less along the entire length of hose in legible block capital letters at least 3 mm high with the following minimum information in the order listed:

- a. The hose manufacturer's identification XXXXX
- b. The words "AIR BRAKE" to identify specific hose application
- c. The hose metric size, such as Size 8
- d. SAE J1402

Example: XXXXX AIR BRAKE Size 8 SAE J1402

In addition, each air brake hose shall be labeled with either an A, AI, All, or AllI, identifying whether the hose has been manufactured to the dimensions of A, AI, All, or AllI hose as shown in Tables 1 and 2. This additional labeling need not appear on the same layline as the above a., b., c., and d. information, but shall have the same minimum requirements of color contrast, spacing, and letter height.

6.2 Fittings

Each field attachable air brake hose fitting shall be permanently etched, embossed, or stamped in legible block capital letters at least 1.5 mm high with the coupling manufacturer's identification, hose size, and whether they are intended for use with Type A, AI, or All hose.

6.3 Assemblies

Each air brake hose assembly shall be identified by means of a band around the hose. The band may move freely along the length of the assembly as long as it is retained by the end fitting. The band shall be permanently etched, embossed, or stamped in legible block capital letters at least 3 mm high with the following information:

- a. The month, day, and year, or the month and year the assembly was made expressed in numerals. For example, 3/1/75 means March 1, 1975, or 3/75 means March 1975.
- b. The assembler's identification and additional information, as required.

7. PERFORMANCE

NOTE 1: All samples subjected to one or more performance tests other than proof pressure and length change shall be destroyed and discarded after completion of the tests and their analysis.

NOTE 2: Burst strength and assembly tensile strength tests are qualification tests and do not imply that the hose assemblies can be used under those conditions.

7.1 Acceptance Performance

Hose or hose assemblies at the time of manufacture shall conform to the following:

7.1.1 End Fittings

End fittings shall be such as to permit conformance to all portions of this recommended practice. After assembly of the end fittings to the hose, the minimum ID of the end fittings or the hose shall not be less than 66% of the minimum hose ID shown in Table 1. All hose assemblies shall pass this requirement prior to conducting any other test in this recommended practice.

7.1.2 Proof Pressure

Assemblies subjected to a pressure test using $2 \text{ MPa} \pm 0.1 \text{ MPa}$ air or nitrogen under water for a minimum of 30 seconds shall show no leaks.

7.1.3 Burst Strength

There shall be no hose burst, leakage, or end fitting separation below 6 MPa when hose or hose assemblies are subjected to a hydrostatic burst test using water.

7.1.4 Assembly Tensile Strength

450 mm long hose assemblies including the fittings shall be subjected to a longitudinal tensile test at a steady rate of $25 \text{ mm/min} \pm 2.5 \text{ mm/min}$ until separation of the hose from the fittings or rupture of the hose occurs. Failure of the 6.3 mm and smaller size shall occur at no less than 1100 N and larger sizes at no less than 1450 N.

7.1.5 Length Change

Test for length change shall be conducted in accordance with ASTM D380 (elongation and contraction) with the original measurement made at 0.1 MPa. The change in length shall be determined at 1.5 MPa and shall be from +5 to -7%.

7.1.6 Adhesion

Tests for adhesion shall be conducted only on original unaged specimens as follows:

7.1.6.1 Adhesion of Fiber Reinforced Hose

Test for adhesion shall be conducted in accordance with ASTM D413 machine method, and the average load required to separate any adjacent layers shall be 1.4 N/mm minimum.

7.1.6.2 Adhesion of Wire Reinforced Hose

The requirements and method of testing cover adhesion for Type AI, AII, and AIII hoses with wire reinforcement shall be as in 7.1.6.1. The integrity of the inner tube adhesion shall be tested by subjecting a length of hose not less than 380 mm long to the following requirements:

Place a steel ball of the size specified in Table 4 in the bore of the hose. One end of the hose shall be attached to a vacuum source and the other end plugged. A vacuum of 17 kPa absolute shall be applied for a period of 5 minutes while the hose is in an essentially straight position. At the conclusion of this period and while still under vacuum, the hose shall be bent 180 degrees to the minimum bend radius in Table 3 in each of two directions 180 degrees apart. After bending and returning to an essentially straight position and while still under vacuum, the ball shall be rolled from end to end of the hose. Failure of the ball to pass freely from end to end shall be indication of separation of the inner tube from the reinforcement layer and shall constitute failure.

Table 4 - Ball size for testing adhesion of wire reinforced hose

Metric Size	5	6.3	8	11	12.5	16
Ball Size (millimeters)	3.5	4.5	6.0	7.5	9.5	12.0

7.2 Qualification Performance

For initial qualification under this specification all of the requirements under Acceptance performance, qualification performance, and flexure test shall be met. Minimum sampling shall be per Table 5, including the specified sequential test procedure.

Table 5 - Minimum sampling and sequential test procedure

Sample No.	Subjected to	Followed by
1	7.1.1 ⁽¹⁾	7.2.1.1 then 7.1.2
2	7.1.1 ⁽¹⁾	7.2.1.2 or 7.2.1.3 ⁽²⁾ then 7.1.2
3	7.2.2.1	--
4	7.1.1 ⁽¹⁾	7.2.2.2 then 7.1.4
5	7.2.2.3	--
6	7.1.1 ⁽¹⁾	7.2.2.4 then 7.1.3
7	7.1.1 ⁽¹⁾	7.1.5 then 7.1.2 and 7.1.3
8	7.1.6	--
9	7.1.1 ⁽¹⁾	Section 8

⁽¹⁾ Couple hose before starting tests or aging.

⁽²⁾ Use test method 7.2.1.3 in place of 7.2.1.2 when rating hose to Extreme Low Temperature Resistance.

7.2.1 Temperature Resistance

7.2.1.1 High Temperature Resistance

The hose portion of a hose assembly shall show no cracks, charring or disintegration externally or internally when straightened after being bent over a form for a period of 70 hours $\pm$ 2 hours while in an air oven at 100 °C $\pm$ 2 °C. The radius of the test form shall be in accordance with Table 3. The external surface of fiber braid covered hoses shall be exempt from inspection for cracks as visual inspection is not practical.

After completion of this test, the hose assembly shall be tested in accordance with 7.1.2.

7.2.1.2 Low Temperature Resistance

The hose shall show no cracks externally or internally when bent 180 degrees over a form having the radius shown in Table 3 after hose and form have been exposed for a period of 70 hours $\pm$ 2 hours in an air circulating chamber at -40 °C $\pm$ 2 °C and while still at this temperature. The hose and form shall be supported by a nonmetallic surface during the entire period. The bend shall be completed in a period of 3 to 5 seconds. The external surface of fiber braid covered hoses shall be exempt from inspection for cracks as visual inspection is not practical.

After completion of this test, the hose assembly shall be tested in accordance with 7.1.2.

7.2.1.3 Extreme Low Temperature Resistance

The hose shall show no cracks externally or internally when bent 180 degrees over a form having the radius shown in Table 3 after hose and form have been exposed for a period of 70 hours $\pm$ 2 hours in an air circulating chamber at -54 °C $\pm$ 2 °C and while still at this temperature. The hose and form shall be supported by a nonmetallic surface during the entire period. The bend shall be completed in a period of 3 to 5 seconds. The external surface of fiber braid covered hoses shall be exempt from inspection for cracks as visual inspection is not practical.

After completion of this test, the hose assembly shall be tested in accordance with 7.1.2.

7.2.2 Resistance to Environment

7.2.2.1 Oil

Specimens prepared from the inner tube and the cover shall show a volume increase when measured after removal from ASTM IRM 903 oil in which it has been immersed for 70 hours $\pm$ 2 hours at 100 °C $\pm$ 2 °C of not more than 100%.

7.2.2.2 Water

Condition hose assembly by immersion in distilled water at room temperature for a period of 168 hours $\pm$ 2 hours while bent over a form having the minimum bend radius shown in Table 3. Ends shall be completely capped during immersion.

After completion of this test, the hose assembly shall be tested in accordance with 7.1.4.

7.2.2.3 Ozone

After being exposed for 70 hours $\pm$ 2 hours in an ozone test cabinet with an atmosphere comprised of air and ozone with an ozone partial pressure of 100 mPa (100 parts of ozone per 100 million parts of air) at standard atmospheric conditions at an ambient temperature of 40 °C $\pm$ 2 °C and while bent over a form having the radius shown in Table 3, the hose shall show no cracking under 7X magnification. This test only applies to elastomeric covered hoses.

7.2.2.4 Salt Spray Test

A hose assembly, while supported or suspended between 15 and 30 degrees from vertical, shall withstand 24 hours $\pm$ 1 hour exposure to salt spray when tested in accordance with ASTM B117. After this exposure, fittings shall show no base metal corrosion except red rust is acceptable in areas of identification stamping and crimp distortions. White corrosion products are acceptable.

After completion of this test, the hose assembly shall be tested in accordance with 7.1.3.

8. FLEXURE TEST

8.1 Preparation of Test Samples

8.1.1 Prior to cutting the hose, apply a layline (of a color distinguishable from that of the hose cover) along the length of the hose (following the natural hose curvature which results from the hose being coiled in a roll) as shown in Figure 1.

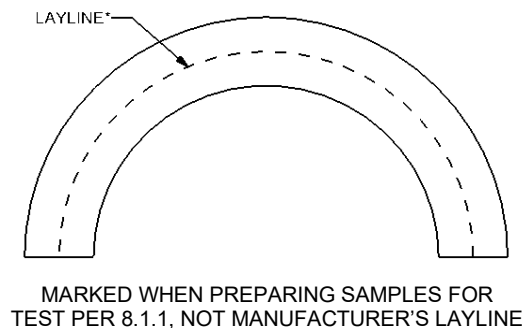


Figure 1 - Hose marking